



Thiadiphosphetane Disulfide as a Metal Extractant Which Shows High Ag⁺ Selectivity


Masaaki Yoshifuji^{†*}, Kozo Toyota[†], Kotaro Shirabe[†],
 Hideshi Iki, Takeshi Nagasaki, and Seiji Shinkai^{*}

[†]Department of Chemistry, Faculty of Science,
 Tohoku University, Aoba, Sendai 980-77, Japan


Department of Chemical Science and Technology, Faculty of Engineering,
 Kyushu University, Fukuoka 812, Japan

Abstracts: It was shown that *cis*-2,4-bis(2,4,6-tri-*tert*-butylphenyl)-1,2,4-thiadiphosphetane 2,4-disulfide (**1**) acts as an excellent Ag⁺-selective extractant. Two-phase solvent-extraction and spectral examination with ¹H and ³¹P NMR established that **1** forms a 1:1 complex with Ag⁺ using the P(=S)-S-P(=S) linkage designed in the rigid four-membered ring.

The metal recognition is achieved by a skillful combination of the "ion-size selectivity" with an ingenious selection of atoms and a spatial arrangement of those atoms. We recently synthesized *cis*-2,4-bis(2,4,6-tri-*tert*-butylphenyl)-1,2,4-thiadiphosphetane 2,4-disulfide (**1**): the X-ray analysis disclosed that **1** has aromatic rings arranged like pincettes and an open space surrounded by three soft S atoms.¹ This structural characteristics strongly tempted us to apply **1** as a metal extractant, particularly that for soft metal ions. Examination with a two-phase solvent-extraction system has established that as expected, **1** shows the high affinity as well as the high selectivity toward Ag⁺.^{2,3}

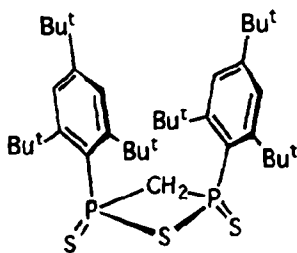

1

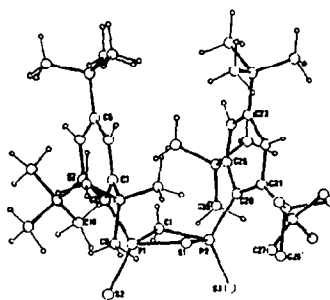X-Ray structure of **1**¹

Two-phase solvent-extraction was carried out at 25 °C with an aqueous solution (25 ml, [metal salt] = 1.1 × 10⁻⁴ mol dm⁻³, pH 5.3 with 0.1 mol dm⁻³ acetate buffer) and a chloroform solution (5 ml, [**1**] = 5.5 × 10⁻⁴ mol dm⁻³). The mole ratio of the metal salt in the aqueous phase and **1** in the organic phase is 1:1. After

shaking for 12 h, the concentration of metal salts in the aqueous phase was analyzed by atomic absorption spectroscopy. The extractability (Ex%) was defined as $[Ag^+]_{org} / [Ag^+]_{total}$. The results are summarized in Table 1. It is seen from Table 1 that **1** has the very high affinity for Ag^+ and the moderate affinity for Pd^{2+} and UO_2^{2+} whereas transition metal ions such as Cu^{2+} , Ni^{2+} , and Fe^{3+} were scarcely extracted. We surveyed the past literatures on the "metal preference" of analogous extractants. Dialkyl sulfides show the high affinity for Pd^{2+} .⁴ "Hard" phosphorous oxides show the high affinity for "hard" UO_2^{2+} .⁵ On the other hand, trialkylphosphine sulfides show the "metal preference" similar to **1** (*i.e.*, $Ag^+ > Pd^{2+} >$ transition metal ions).⁶ The results manifest that in **1** the essential functional group used for metal-binding is the P=S group but not the -S- group. It is now clear that **1** acts as a useful Ag^+ -selective extractant because of the P=S $\cdots Ag^+$ interaction.

Table 1. Extraction of transition metal cation by **1**.

Metal Salt	Ex%
$Cu(NO_3)_2$	trace
$Ni(NO_3)_2$	trace
$Fe(NO_3)_3$	trace
$Fe(NO_3)_3$	42.1 ^b
$AgNO_3$	86.6
$AgNO_3$	98.4 ^b
$PdCl_2$	8.3
$PdCl_2$	14.2 ^b
$K_4[UO_2(CO_3)_3]$	15.2 ^c

^a pH = 5.3 with 0.1 mol dm⁻³ acetate buffer.

^b Toluene was used as an organic phase.

^c pH = 5.9 with 0.01 mol dm⁻³ acetate buffer.

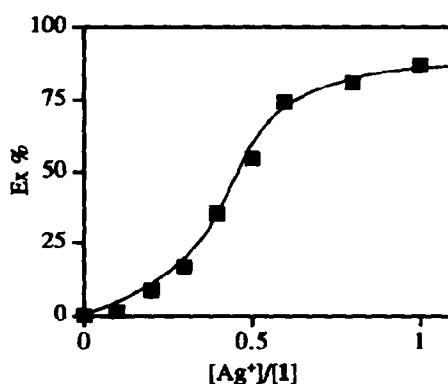


Fig. 1. Plot of Ex% vs. $[Ag^+] / [1]$ in two-phase solvent-extraction. **1** (5.5×10^{-4} mol dm⁻³) was maintained constant.

Subsequently, we estimated Ag^+ -extraction properties more in detail. Fig. 1 shows a plot of Ex% against $[\text{Ag}^+]/[1]$ (where $[1]$ is maintained constant). The Ex% is almost saturated at $[\text{Ag}^+]/[1] = 1.0$, indicating that the extracted species has 1:1 stoichiometry. However, the plot shows a sigmoidal curve but not a simple saturation curve. Probably, this peculiar dependence is caused by the aggregation of AgClO_4 in chloroform.

In ^{31}P NMR spectroscopy the δ_{P} (46.3 ppm in C_6D_6 at 25°C in the absence of AgClO_4) shifted to lower magnetic field and was saturated at 62.2 ppm. Fig. 2 shows a plot of δ_{P} against $[\text{Ag}^+]/[1]$; the shift saturation occurs at $[\text{Ag}^+]/[1] = 1.0$ and the sigmoidal dependence is again observable at $[\text{Ag}^+]/[1] = 0 \sim 1.0$ region. In ^1H NMR spectroscopy (in C_6D_6 at 25°C) the PCH_2P methylene protons appear at 4.41 and 4.77 ppm. To assign the geminal protons we measured NOE with respect to the *tert*-Bu protons but failed because of the weak correlation. As shown in Fig. 3, the δ_{H} at higher magnetic field shifts to higher magnetic field while the δ_{H} at lower magnetic field shifts to lower magnetic field as the Ag^+ concentration increases. The breakpoints are again observed at $[\text{Ag}^+]/[1] = 1.0$. According to the X-ray structure of **1**,¹ the distance between the two S atoms is 4.51 Å. Even though taking the van der Waals radius of S (1.80 Å), this distance is a little too long to tweeze Ag^+ (radius 1.15 Å) with the two S atoms. It is reasonable to consider, therefore, that upon the Ag^+ binding the two P=S groups are a little expanded and consequently the aromatic ring pincettes are closed. In this motion one of the two PCH_2P protons is shielded and the other deshielded.

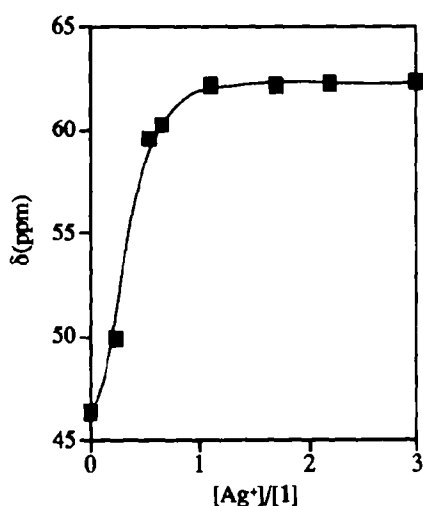


Fig. 2. Plot of δ_{P} vs. $[\text{Ag}^+]/[1]$ in C_6D_6 at 25°C .

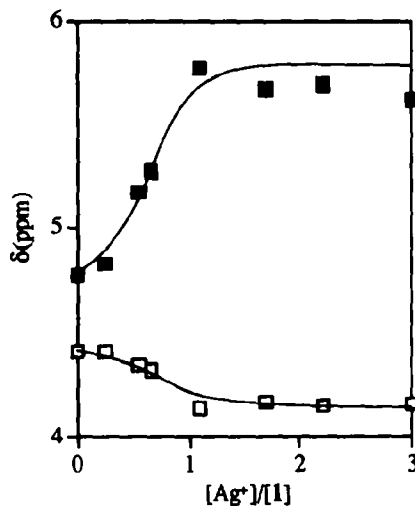


Fig. 3. Plots of δ_{H} for the two PCH_2P methylene protons vs. $[\text{Ag}^+]/[1]$ in C_6D_6 at 25°C .

In conclusion, the present paper reveals that the $\text{P}(=\text{S})\text{-S-P}(=\text{S})$ linkage designed in a rigid four-membered ring serves as an excellent Ag^+ -selective extractant forming a 1:1 complex. This is a new and unique entry for the Ag^+ -selective metal receptor.

References

1. Toyota, K.; Yoshifuji, M.; Hirotsu, K. *Chem. Lett.*, **1990**, 643.
2. For extraction of heavy metal ions with "soft"-atom-containing extractants see Beamish, F. E.; *Talanta*, **14**, 991, 1967; Mojaki, M. *Chemia Analityczna*, **24**, 207, 1979; Gindin, L. M. *Ion Exchange and Solvent Extraction*; Marinsky, J. A.; Marcus, Y., Eds.; Marcel Dekker: New York, 1981, Vol. 8, p. 311.
3. For Ag⁺-selective extractants see Blake, A. J.; Reid, G.; Schröder, M. *J. Chem. Soc., Chem. Commun.*, **1992**, 1074; Clarkson, J.; Yagbasan, R.; Blower, P. J.; Rawle, S. C.; Cooper, S. R. *ibid.*, **1987**, 950; Sato, M.; Kubo, M.; Ebine, S.; Akabori, S. *Bull. Chem. Soc. Jpn.*, **57**, 421, 1984, and references cited therein. They are thiacycrown ether derivatives.
4. Nikolaev, A. V.; Torgov, V. G.; Mikhailov, V. A.; Andrievski, V. N.; Bakovets, K. A.; Bondarenko, M. F.; Gil'bert, E. N.; Kotlyarevskii, I. L.; Mardezova, G. N.; Shatskaya, S. S. *Izv. Sib. Otd. Akad. Nauk SSSR. Ser. Khim. Nauk*, **9**, 54, 1970.
5. Pozas-Tormo, R.; Moreno-real, L.; Martinez-Lara, M.; Bruque-Gamez, S. *Inorg. Chem.*, **26**, 1442, 1987; Cromer, D. T.; Ryan, R. R.; Karthikeyar, S.; Paine, R. T. *Inorg. Chim. Acta*, **172**, 165, 1990.
6. Hitchcock, R. B.; Dean, J. A.; Handley, H. *Anal. Chem.*, **35**, 254, 1963.

(Received in Japan 31 March 1994; accepted 28 May 1994)