

This article was downloaded by: [CAS Chinese Academy of Sciences]

On: 16 March 2011

Access details: Access Details: [subscription number 931694536]

Publisher Taylor & Francis

Informa Ltd Registered in England and Wales Registered Number: 1072954 Registered office: Mortimer House, 37-41 Mortimer Street, London W1T 3JH, UK



Spectroscopy Letters

Publication details, including instructions for authors and subscription information:

<http://www.informaworld.com/smpp/title~content=t713597299>

Emission Spectra of Tb³⁺:PVA Polymer Films

G. Seeta Rama Raju^a; S. Buddhudu^a; A. Varada Rajulu^b; L. Ganga Devi^b

^a Department of Physics, S.V. University, Tirupati, India ^b Department of Polymer Science, S.K. University, Anantapur, India

To cite this Article Raju, G. Seeta Rama , Buddhudu, S. , Rajulu, A. Varada and Devi, L. Ganga(2006) 'Emission Spectra of Tb³⁺:PVA Polymer Films', Spectroscopy Letters, 39: 5, 487 – 495

To link to this Article: DOI: 10.1080/00387010600824736

URL: <http://dx.doi.org/10.1080/00387010600824736>

PLEASE SCROLL DOWN FOR ARTICLE

Full terms and conditions of use: <http://www.informaworld.com/terms-and-conditions-of-access.pdf>

This article may be used for research, teaching and private study purposes. Any substantial or systematic reproduction, re-distribution, re-selling, loan or sub-licensing, systematic supply or distribution in any form to anyone is expressly forbidden.

The publisher does not give any warranty express or implied or make any representation that the contents will be complete or accurate or up to date. The accuracy of any instructions, formulae and drug doses should be independently verified with primary sources. The publisher shall not be liable for any loss, actions, claims, proceedings, demand or costs or damages whatsoever or howsoever caused arising directly or indirectly in connection with or arising out of the use of this material.

Emission Spectra of Tb³⁺:PVA Polymer Films

G. Seeta Rama Raju and S. Buddhudu

Department of Physics, S.V. University, Tirupati, India

A. Varada Rajulu and L. Ganga Devi

Department of Polymer Science, S.K. University, Anantapur, India

Abstract: This paper reports on the development and optical analysis of Tb³⁺-doped polyvinyl alcohol (PVA) films. A reference PVA film has also been prepared for which X-ray diffraction (XRD) spectral profile has been carried out; it was found that this polymer possesses a semi crystalline nature. Spectral analysis of the Tb³⁺:PVA polymer film has been made based on the measurement of the excitation, emission, and decay curves of the emission transitions (⁵D₄ → ⁷F_{6,5,4&3}). Under a UV source (254 nm), a bright green emission was noticed from the surface of Tb³⁺:PVA film. The current study reveals that this terbium polymer film could be suggested as a novel green luminescent material.

Keywords: Doped films, emission, excitation, fluorescent systems, polyvinyl alcohol, terbium

INTRODUCTION

It is well-known that optical properties of different rare-earth ion-doped materials are found to be dependent on the host matrices used.^[1–5] In recent times, more emphasis has been made toward the development of polymer-based luminescent optical materials.^[6–9] From the literature it has been reported that a prominent green luminescence could be obtained from the terbium (Tb³⁺)-doped glasses and phosphors.^[10–15] Polyvinyl alcohol

Received 15 March 2006, Accepted 25 May 2006

Address correspondence to S. Buddhudu, Department of Physics, S.V. University, Tirupati 517502, India. E-mail: drsb99@hotmail.com

(PVA) is widely known as a promising material for its potential uses in industry, pharmaceuticals, film coatings, magnetic media, and so forth.^[16–23] Because there has not been any work done in literature on the Tb³⁺ ion-doped polyvinyl alcohol (PVA)-based polymer film, we have undertaken this work for its spectroscopic analysis from the measurement of absorption spectrum, excitation and emission spectra along with the lifetimes of the emission transitions (⁵D₄ → ⁷F_{6,5,4,3}) in the visible wavelength range with an excitation at 374 nm. Even under UV source, these Tb³⁺-doped PVA polymer films have displayed bright green emission from their surfaces. In order to undertake the analysis of Tb³⁺:PVA films, we have followed Tb³⁺-doped sol-gel derived films and polysiloxanes.^[24–30]

MATERIALS AND METHODS

In the current work, undoped and terbium-doped (0.1 mol%) PVA (with a molecular weight (MW) of 14,000, Loba Chemie pvt. Ltd) polymer films were developed from aqueous solutions by means of a film-casting method. Polymer films with a uniform thickness of 1 mm were cast by using a thin-layer chromatography (TLC) spreader. Regarding the preparation of Tb³⁺ ions-doped PVA films, TbCl₃ (MW = 373.38 g, Aldrich) salt was dissolved separately in a beaker containing double-distilled water at room temperature, then this rare-earth salt-mixed solution was mixed with the PVA solution, and this resultant rare-earth-doped PVA solution was stirred with a magnetic stirrer continuously to ensure homogeneity in the solution mixture, and this solution was used on a TLC spreader in order to produce a 1-mm-thick Tb³⁺:PVA polymer film 15 cm long and 10 cm wide. These films were cut into different sizes and in the present work; we have used films of 50 mm × 20 mm × 1 mm dimensions for its optical characterization. The XRD spectrum of PVA film was recorded on a X' pert PRO X-ray diffractometer with CuK_α (1.54056 Å) radiation that was operated at 40 kV with about 50 mA anode current. The refractive indices of the reference PVA film have been measured by using Abbe refractometer at three different wavelengths (479.99 nm of Cd-lamp, 589.3 nm of Na-lamp, 643.85 nm of Cd-lamp) and are given in the Table 1. Absorption spectra of reference PVA film and

Table 1. Physical quantities of the PVA polymer film

Molecular weight (MW) g	14,000
Density (d)	1.35 g/cc
Tb ³⁺ ion concentration, N _{Tb³⁺}	5.808 × 10 ¹⁸ (ions/cm ³)
n _d at 589.30 nm	1.340
n _F at 479.99 nm	1.344
n _C at 643.85 nm	1.337

Tb³⁺:PVA films were recorded on a Jasco Absorption Spectrophotometer in the wavelength range of 200–500 nm. Both excitation and emission spectra of Tb³⁺:PVA polymer films were recorded in the wavelength range 200–650 nm on a SPEX Fluorolog-2 Fluorimeter (model II) attached to a Xe-Arc Lamp (150 W). This fluorescence system employs the Datamax Software in acquiring spectral data of the samples used. For the measured emission bands, lifetimes were obtained on the same fluorimeter with an Xe-flash lamp and a phosphorimeter attachment to the main system with a control system while measuring the decay curves of these emission bands. All the above spectra are recorded at room temperature. The physical characteristic parameters of the reference PVA film are given in Table 1.

RESULTS AND DISCUSSION

Tb³⁺:PVA film has shown a prominent green emission from its surface under UV source as shown in Fig. 1. The measured X-ray diffraction (XRD) spectral profile of the Tb³⁺:PVA polymer film is given in Fig. 2, which confirms the semicrystalline nature of the polymer, as was reported previously in literature.^[21,22] The measured refractive indices are used in evaluating the Cauchy's constants (A&B), and the Cauchy's formula of refractive index (n), as a function of wavelength (λ), is given by $n(\lambda) = A + B/\lambda^2$, which depends on the wavelength employed,^[24] and the computed values of the Cauchy's constants are $A = 1.32955$ and $B = 3630.4 \text{ nm}^2$. The theoretical plot of refractive indices obtained through a Cauchy's formula as function of wavelength is shown in Fig. 3. With these Cauchy's constants, the correlation between the measured and computed refractive indices at three wavelengths have been found to be good enough. The optical dispersion (ν_d^{-1}) of this polymer film has been evaluated based on the refractive indices according to the formula $\nu_d^{-1} = (n_F - n_C)/(n_d - 1)$ ^[25] and the calculated



Figure 1. Green luminescent Tb³⁺:PVA polymer film under a UV lamp.

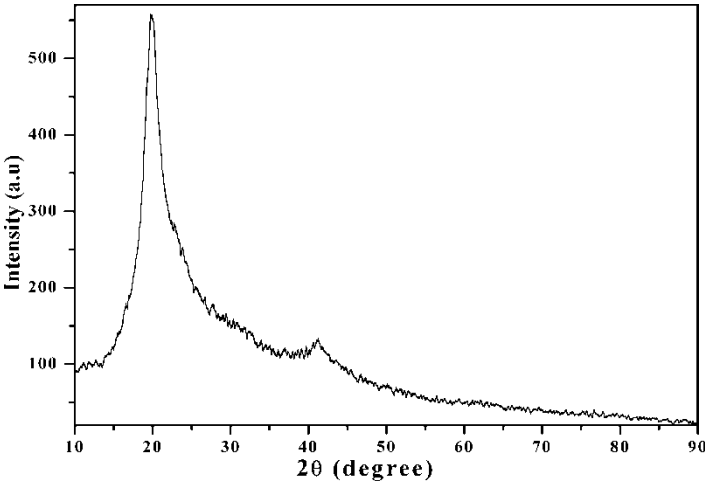


Figure 2. XRD profile of the PVA polymer film.

value is 0.0206. Absorption spectra of the reference PVA film and Tb^{3+} :PVA films are shown in Figs. 4a and 4b, respectively. From the PVA absorption spectrum (Fig. 4a), it is noticed that there is a weak absorption band at 275 nm, which is in agreement with the reported value.^[23] From Fig. 4b, it is observed that there exists a strong absorption band at 263 nm for the Tb^{3+} :PVA besides nine more weaker absorption bands at 284 nm, 295 nm,

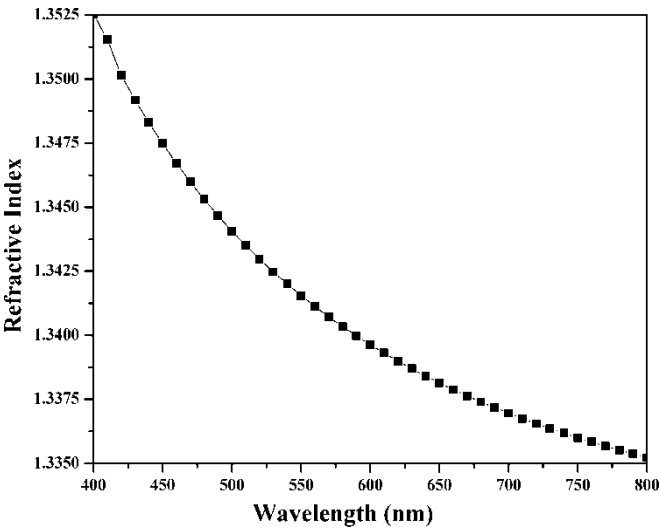


Figure 3. Refractive indices of PVA polymer film from cauchy's method.

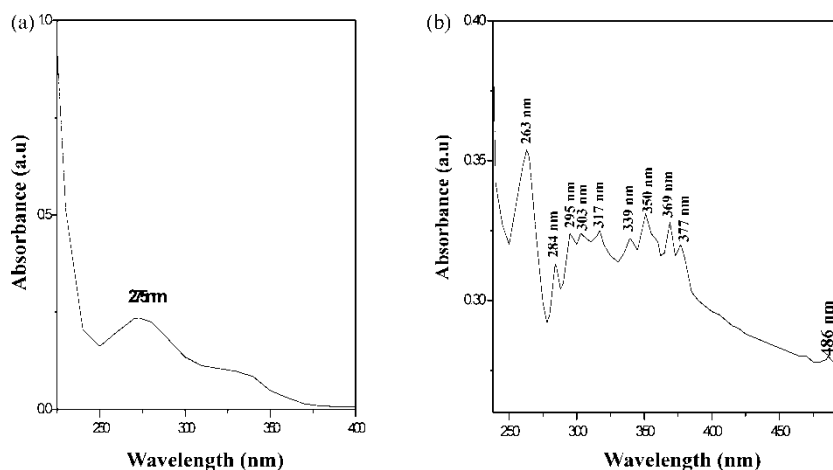


Figure 4. (a) Absorption spectrum of pure PVA film. (b) Absorption spectrum of Tb³⁺:PVA film.

303 nm, 317 nm, 339 nm, 350 nm, 369 nm, 377 nm, and 486 nm, respectively, and those have appropriately been assigned to the electronic transitions such as (⁷F₆ → ⁵I₅) at 263 nm, (⁷F₆ → ⁵I₈) at 284 nm, (⁷F₆ → ⁵H₅) at 295 nm, (⁷F₆ → ⁵H₆) at 303 nm, (⁷F₆ → ⁵H₇) at 317 nm, (⁷F₆ → ⁵L₆) at 339 nm, (⁷F₆ → ⁵L₉) at 350 nm, (⁷F₆ → ⁵L₁₀) at 369 nm, (⁷F₆ → ⁵G₆) at 377 nm,

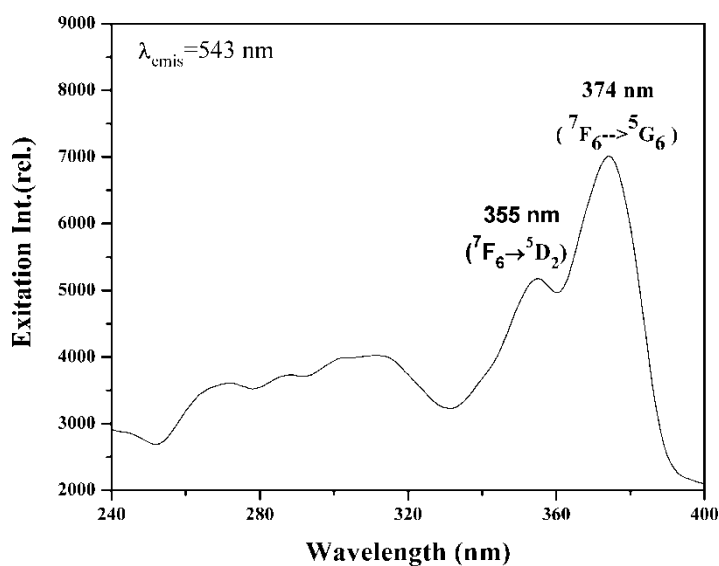


Figure 5. Excitation spectrum of Tb³⁺:PVA polymer film.

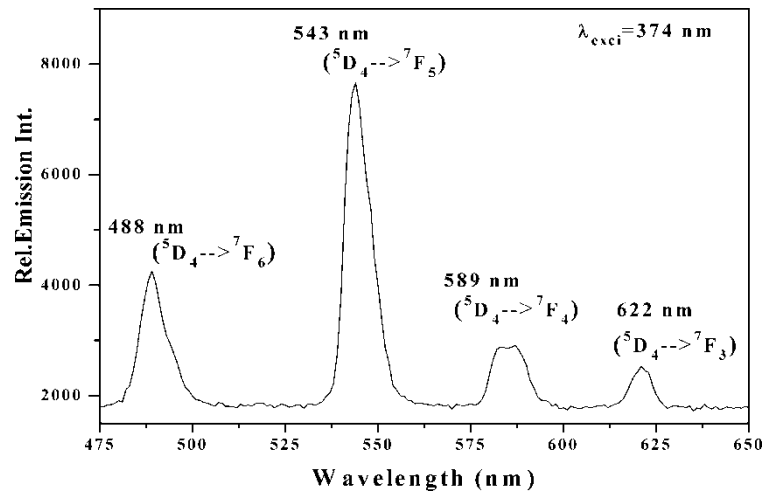


Figure 6. Emission spectrum of Tb³⁺:PVA polymer film.

and (${}^7F_6 \rightarrow {}^5D_4$) at 486 nm, which are also in agreement with the reported values.^[15] The excitation spectrum (240–400 nm) of the terbium-doped polymer is shown in Fig. 5. It consists of a number of lines in the region from 240 nm to 320 nm, a weak band at 355 nm to the spin forbidden transition and a strong band at 374 nm to the spin allowed transition of Tb³⁺, which belong to the electronic transitions (${}^7F_6 \rightarrow {}^5D_2$) and (${}^7F_6 \rightarrow {}^5G_6$), respectively. The lines correspond with absorption of the forbidden f-f

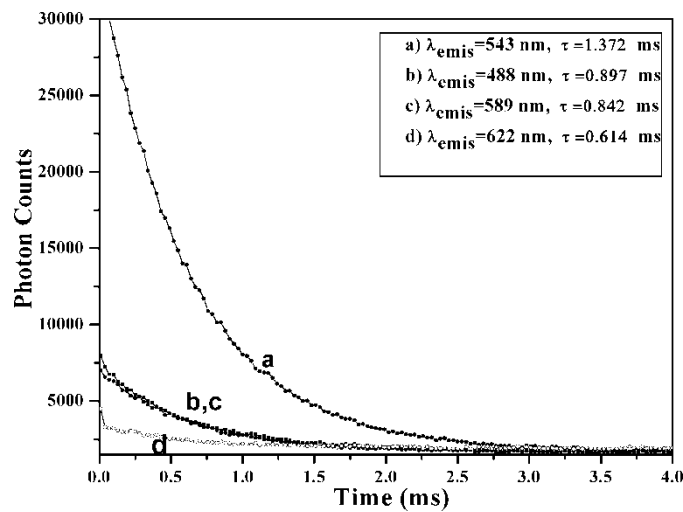


Figure 7. Decay curves for emission transitions of Tb³⁺:PVA polymer film.

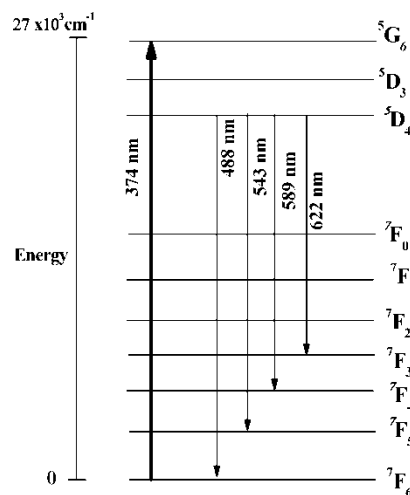


Figure 8. Emission mechanism in Tb³⁺:PVA polymer film.

transitions of Tb³⁺ ions. Emission spectrum of this polymer film is shown in Fig. 6, which demonstrates an intense *green* emission ($^5\text{D}_4 \rightarrow ^7\text{F}_5$) at 543 nm, a medium intense *blue* emission ($^5\text{D}_4 \rightarrow ^7\text{F}_6$) at 488 nm, a weak *orange* emission ($^5\text{D}_4 \rightarrow ^7\text{F}_4$) at 589 nm, and a weaker *red* emission ($^5\text{D}_4 \rightarrow ^7\text{F}_3$) at 622 nm. Among these four emission bands, the green emission band ($^5\text{D}_4 \rightarrow ^7\text{F}_5$) is a magnetic dipole transition satisfying the selection rule of $\Delta J = \pm 1$. Figure 7 presents the exponential decay curves of the Tb³⁺-doped PVA polymer film for four emission transitions with the ($^5\text{D}_4 \rightarrow ^7\text{F}_5$) transition having a longer lifetime of 1.372 ms; other three emission transitions have the lifetimes $^5\text{D}_4 \rightarrow ^7\text{F}_6$ (0.897 ms), $^5\text{D}_4 \rightarrow ^7\text{F}_4$ (0.842 ms), and $^5\text{D}_4 \rightarrow ^7\text{F}_3$ (0.614 ms). An energy level scheme is given in Fig. 8 to explain the mechanism involved in the emission process in the Tb³⁺:PVA polymer film with a pump wavelength at 373 nm, which belongs to the transition of ($^7\text{F}_6 \rightarrow ^5\text{G}_6$). The emission intensity of $^5\text{D}_3$, $^5\text{D}_4 \rightarrow ^7\text{F}_0$, $^7\text{F}_1$, $^7\text{F}_2$ were weak enough and were neglected.

CONCLUSIONS

In summary, it could be stated that we have successfully developed Tb³⁺:PVA polymer films, and their optical properties have been carried out systematically based on their spectral profiles. Apart from this, under a UV source these films have shown bright green luminescence from their surfaces. In view of these, it could be suggested as a novel optical material of significant technical importance as luminescent systems for various display applications.

REFERENCES

1. Sloff, L. H.; Blaaderen, A. V.; Polman, A.; Hebbink, G. A.; Klink, S. I.; VanVeggel, F. C. J. M.; Reinhoudt, D. N.; Hofstraat, J. W. Rare-earth doped polymers for planar optical amplifiers. *J. Appl. Phys.* **2002**, *91*, 3955–3980.
2. Tanabe, S.; Ohyagi, T.; Soga, N.; Honda, T. H. Compositional dependence of Judd-Ofelt parameters of Er^{3+} ions in alkali-metal borate glasses. *Phys. Rev. B* **1992**, *46*, 3305–3310.
3. Weber, M. J. Science and technology of laser glass. *J. Non-Cryst. Solids* **1990**, *123*, 208–222.
4. Weber, M. J.; Ziegler, D. C.; Angell, C. A. Tailoring stimulated emission cross sections of Nd^{3+} laser glass: observation of large cross sections of BiCl_3 glasses. *J. Appl. Phys.* **1982**, *53*, 4344–4350.
5. Weber, M. J.; Saroyan, R. A. Optical properties of Nd^{3+} in meta phosphate glasses. *J. Non-Cryst. Solids* **1981**, *44*, 137–148.
6. Sosa, F. R.; Flores, H. R. M.; Rodriguez, T.; Munoz, F. A. Optical properties and Judd-Ofelt intensity parameters of Eu^{3+} in PMMA: PAAC co polymer samples. *Rev. Mex. Fis.* **2003**, *49* (6), 519–524.
7. Xu, X. S.; Haiming; Zhang, Q. Optical-transition probabilities of Nd^{3+} ions in polymer optical fibers. *Opt. Commun.* **2001**, *199*, 369–373.
8. Smirnov, V. A.; Philippova, O. E.; Sukhadolski, G. A. Multiplets in polymer gels. Rare-earth metal ions in luminescent study. *Macro. Mol.* **1998**, *31* (4), 1162–1167.
9. Rajagopalan, P.; Tsatsas, A. T. Synthesis and near infrared properties of rare earth ionomers. *J. polym. Sci.* **1996**, *34*, 151–161.
10. Miao, Y.; Liu, J.; Hou, F.; Jiang, C. Determination of adenosine disodium triphosphate (ATP) using norfloxacin- Tb^{3+} as a fluorescence probe by spectrofluorimetry. *J. Lumin.* **2006**, *116*, 67–72.
11. Vedda, A.; Chiodini, N.; Martino, D. D.; Fasoli, M.; Griguta, L.; Moretti, F.; Rosetta, E. Thermally stimulated luminescence Ce and Tb doped SiO_2 sol-gel glasses. *J. Non-Cryst. Solids* **2005**, *351*, 3699–3703.
12. Yamazaki, M.; Kojima, K. Long-lasting after glow in Tb^{3+} -doped SiO_2 - Ga_2O_3 - CaO - Na_2O glasses and its sensitization by Yb^{3+} . *Solid State Commun.* **2004**, *130*, 637–639.
13. Cheng, S. D.; Kam, C. H.; Buddhudu, S. Enhancement of green emission from Tb^{3+} : GdOBr phosphor with Ce^{3+} ion co-doping. *Mater. Res. Bull.* **2001**, *36*, 1131–1137.
14. Aruna, V.; Buddhudu, S. Spectral properties of Ib^{3+} : B_2O_3 - P_2O_5 - R_2SO_4 glasses. *Mater. Lett.* **1998**, *36*, 24–28.
15. Sekita, M.; Miyazawa, Y.; Morita, S.; Sekiwa, H.; Sato, Y. Strong Tb^{3+} emission of TbAlO_3 at room temperature. *Appl. Phys. Lett.* **1994**, *65* (19), 2380–2382.
16. Wong, S. S.; Altinkaya, S. A.; Mallapragada, S. K. Drying of Semi crystalline polymers: Mathematical modeling and experimental characteristics of poly vinyl alcohol films. *Polymer* **2005**, *45*, 5151–5161.
17. Alsoy, S.; Duda, J. L. Modeling of multi component drying of polymer films. *A. I. Che J.* **1999**, *45*, 896–905.
18. Alsoy, S.; Duda, J. L. Drying of solvent coated polymer films. *Dry Technol.* **1998**, *16*, 15–44.
19. Yamaura, K.; Noriyasu, k.; Suzuki, M.; Tanigami, T. S.; Shuji, M. Properties of mixtures of silk fibroin/syndiotacticrich poly vinyl alcohol. *J. Appl. Polym. Sci.* **1990**, *41*, 2409–2425.
20. Tawansi, A.; Migahed, M. D.; Hamid, M. I. A. E. L. Electrical conduction of poly vinyl alcohol films. *Poly. Sci. B.* **1986**, *24*, 2631–2642.

21. Yang, C. C.; Lin, S. J.; Hsu, S. T. Synthesis and characterization of alkaline poly vinyl alcohol and polyepichlorohydrin blend polymer electrolytes and performance in electrochemical cells. *J. Power Sources* **2003**, *122*, 210–218.
22. Yang, C. C. Chemical composition and XRD analysis for alkaline composite PVA Polymer electrolyte. *Mater. Lett.* **2003**, *58*, 33–38.
23. Hemantha Kumar, G. N.; Lakshmana Rao, J.; Gopal, N. O.; Narasimhulu, K. V.; Varada Rajulu, A. Spectroscopic investigations of Mn²⁺ ions doped poly vinyl alcohol films. *Polymer* **2004**, *45*, 5407–5415.
24. Yongkee, K. Physical, chemical and optical properties of aqueous L-arginine phosphate (LAP) solution. *J. Mater. Sci.* **2000**, *35*, 873–880.
25. Aruna, V.; Sooraj Hussain, N.; Rajamohana Reddy, K.; Annapurna, K.; Buddhudu, S. Spectral properties of Eu³⁺:B₂O₃-P₂O₅-R₂SO₄ glasses. *Mater. Lett.* **1997**, *33*, 201–206.
26. Balakrishnan, S.; Gun'ko, Y. K.; Perova, T. S.; Rafferty, A.; Astrova, E. V.; Moore, R. A. Porous silicon – rare earth doped xerogel and glass composites. *Phys. Status Solidi A* **2005**, *202* (8), 1693–1697.
27. Gaponenko, N. V.; Molchan, I. S.; Sergeev, O. V.; Thompson, G. E.; Pakes, A.; Skelton, P.; Kudrawiec, R.; Bryja, L.; Misiewicz, J.; Pivin, J. C.; Hamilton, B.; Stepanovaf, E. A. Enhancement of green terbium-related photoluminescence from highly doped microporous alumina xerogels in mesoporous anodic alumina. *J. Electrochem. Soc.* **2002**, *149* (2), H49–H52.
28. Gaponenko, N. V.; Sergeev, O. V.; Borisenko, V. E.; Pivin, J. C.; Skeldon, P.; Thompson, G. E.; Hamilton, B.; Misiewicz, J.; Bryja, L.; Kudrawiec, R.; Stupak, A. P.; Stepanova, E. A. Terbium photoluminescence in polysiloxane films. *Mater. Sci. Eng. B* **2001**, *81* (1), 191–193(3).
29. Pivin, J. C.; Gaponenko, N. V.; Molchan, I.; Kudrawiec, R.; Misiewicz, J.; Bryja, L.; Thompson, G. E.; Skeldon, P. Comparison of terbium photoluminescence from ion implanted and sol-gel-derived films. *J. Alloys Compd.* **2002**, *341* (1), 272–274(3).
30. Gaponenko, N. V.; Molten, I. S.; Gaponenko, S. V.; Mudryi, A. V.; Lyutich, A. A.; Misiewicz, J.; Kudrawie, R. Luminescence of Eu³⁺ and Tb³⁺ ions in the structure microporous xerogel/mesoporous anodic aluminum oxide. *J. Appl. Spectrosc.* **2003**, *70* (1), 59–64.